arXiv:1208.3128v1 [cond-mat.supr-con] 14 Aug 2012

No magnetic pairing mechanism in cuprate superconductors

Guo-meng Zhao[1,*] and A. S. Alexandrov[2,3]
[1]*Department of Physics and Astronomy, California State University, Los Angeles, CA 90032, USA*
[2]*Department of Physics, Loughborough University, Loughborough, LE11 3TU, U.K.*
[3]*Instituto de Fisica "Gleb Wataghin", Universidade Estadual de Campinas,*
UNICAMP 13083-970, Campinas, Sao Paulo, Brazil

We have analyzed scanning tunneling spectra of two electron-doped cuprates $\mathrm{Pr_{0.88}LaCe_{0.12}CuO_4}$ ($T_c = 21$ K and 24 K) and compared them with tunneling spectrum of hole-doped $\mathrm{La_{1.84}Sr_{0.16}CuO_4}$ and effective electron-boson spectral function of hole-doped $\mathrm{La_{1.97}Sr_{0.03}CuO_4}$ (extracted from angle-resolved photoemission spectrum). We have also compared tunneling spectra and angle-resolved photoemission spectra for hole-doped $\mathrm{Bi_2Sr_2CaCu_2O_8}$. These results unambiguously rule out d-wave magnetic pairing mechanism in both electron- and hole-doped cuprates. In contrast, the polaron-bipolaron theory of superconductivity, which is based on realistic electron-electron correlation and strong long-range electron-phonon interaction, is compatible with most experimental results including the Cooper pairing and large Fermi surface observed in optimally doped and overdoped cuprates.

Developing the microscopic theory for high-T_c superconductivity is one of the most challenging problems in condensed matter physics. Twenty-six years after the discovery of high-T_c superconductivity by Bednorz and Müller [1], no consensus on the microscopic pairing mechanism has been reached despite tremendous experimental and theoretical efforts. There are essentially two opposite views about the pairing mechanism. Many researchers believe that antiferromagnetic fluctuations predominantly mediate the electron pairing [2] mainly because of the d-wave order-parameter symmetry probed by surface and phase-sensitive experiments [3]. In contrast, other researchers insist that strong electron-phonon coupling is mainly responsible for high-temperature superconductivity in cuprates. The bipolaronic theory of superconductivity [4], which is based on strong electron correlation and significant electron-phonon interaction (EPI), has gained strong support from various experimental results. In particular, extensive studies of unconventional oxygen-isotope effects in hole-doped cuprates have clearly shown strong EPI and the existence of polarons/bipolarons in both normal and superconducting states [5–13]. Neutron scattering [14–16], angle-resolved photoemission (ARPES) [17, 18], pump-probe [19], and optical specroscopies [20–23] have also demonstrated strong electron-phonon coupling. Further, ARPES data [24] and tunneling spectra [25–30] have consistently provided direct evidence for strong coupling to multiple-phonon modes in hole-doped cuprates.

Despite the fact that so many experiments have supported polaronic/bipolaronic superconductivity, the bipolaronic theory of superconductivity has not been generally accepted. There are several reasons for this. First, much attention has been paid to bipolaronic theories based on strong short-range Holstein-type EPI. These theories fail to predict a high critical temperature because the bipolarons are too heavy and localization of the heavy bipolarons is inevitable. Secondly, there is strong experimental evidence for the Cooper pairing rather than the real-space pairing in optimally and overdoped cuprates [11]. Thirdly, ARPES, optical, and transport experiments have consistently pointed towards a large Fermi surface in overdoped cuprates [11]. These results appear to argue against the bipolronic theory of superconductivity. However, an analytical multi-polaron model of high-temperature superconductivity in highly polarizable ionic lattices has recently been proposed with generic (bare) Coulomb and Fröhlich EPI avoiding any ad-hoc assumptions on their range and relative magnitude [31]. The generic Hamiltonian comprising any-range Coulomb repulsion and the Fröhlich EPI can be reduced to a short-range $t - J_p$ model at very large lattice dielectric constant, $\epsilon_0 \to \infty$, for the moderate and strong EPI. In this limit the bare static Coulomb repulsion and EPI negate each other giving rise to a novel physics described by the polaronic $t - J_p$ model with a short-range polaronic spin exchange J_p of phononic origin [31]. Moreover, if one considers realistic finite ϵ_0, the cancelation of the bare Coulomb repulsion by the Fröhlich EPI is not complete so that a residual on-site repulsion $\tilde{U}$ of polarons could be substantial if the size of the Wannier (atomic) orbitals is small enough [32]. The residual Hubbard $\tilde{U}$ drives the system to undergo a crossover from Bose-Einstein condensation (BEC) to the Cooper pairing [32]. This naturally reconciles the polaron-bipolaron theory of superconductivity with the Cooper pairing and the large Fermi surface observed in optimally doped and overdoped cuprate superconductors [11].

On the other hand, many researchers still maintain the d-wave magnetic pairing mechanism, allegedly supported by some highly publicized experimental papers [33–35]. In one of the papers [34], the authors have used an unrealistic parameter, which overestimates the magnetic coupling constant by two orders of magnitude [36]. Other two papers [33, 35] reported the combined neutron and tunneling data for two electron-doped $\mathrm{Pr_{0.88}LaCe_{0.12}CuO_{4-y}}$ (PLCCO) crystals with different superconducting transition temperatures (21 and 24 K).

These data seemingly suggest that the energies of the magnetic resonance modes are the same as those of the bosonic modes revealed in the second derivative ($\mathrm{d}^2I/\mathrm{d}V^2$) of electron tunneling current (I) with respect to bias voltage (V). They thus conclude that the magnetic resonance modes rather than phonons mediate electron pairing in electron-doped cuprates [33, 35]. However, one of us (GMZ) [30] has already pointed out a basic mistake in the data analyses of Ref. [33] and shown that the combined neutron and tunneling data actually disprove this magnetic pairing mechanism. Despite citing Ref. [30], the same basic mistake has been repeated in Ref. [35]. Based on the repeated incorrect analyses, these authors concluded that their data support d-wave magnetic pairing mechanism.

Here we re-analyze scanning tunneling spectra of two electron-doped cuprates $\mathrm{Pr_{0.88}LaCe_{0.12}CuO_4}$ ($T_c = 21$ K and 24 K) and compare them with tunneling spectrum of hole-doped $\mathrm{La_{1.84}Sr_{0.16}CuO_4}$ and effective electron-boson spectral function of hole-doped $\mathrm{La_{1.97}Sr_{0.03}CuO_4}$ (extracted from angle-resolved photoemission spectrum). Our data analysis along with other independent tunneling and ARPES data consistently rules out d-wave magnetic pairing mechanism in both electron- and hole-doped cuprates. This is in agreement with recent analytical [37] and numerical (Monte-Carlo) [38, 39] studies that cast serious doubts on the possibility of high temperature superconductivity from repulsive interactions only. This is also in accord with optical experiments [22] which show that the electron-boson spectral function $\alpha^2(\omega)F(\omega)$ is independent of magnetic field, in contradiction with the theoretical prediction based on the magnetic pairing mechanism (see Fig. 9 of Ref. [22]).

It has been well established [26, 28, 29, 40, 41]) that the energies of the dip positions (rather than the peak positions) in $\mathrm{d}^2I/\mathrm{d}V^2$ correspond to the energies of the modes strongly coupled to electrons. In Fig. 1, we adopt this well-established protocol to identify the mode energies from the $\mathrm{d}^2I/\mathrm{d}V^2$ spectra of two electron-doped samples. For the electron-doped sample with $T_c = 21$ K, the mode energies identified from the $\mathrm{d}^2I/\mathrm{d}V^2$ spectrum below 35 meV are 6.0 meV and 16.7 meV (indicated by the arrows). For the electron-doped sample with $T_c = 24$ K, the mode energy identified from the $\mathrm{d}^2I/\mathrm{d}V^2$ spectrum between 7 and 28 meV is 16.5 meV. It is apparent that the mode energies revealed in the $\mathrm{d}^2I/\mathrm{d}V^2$ spectra of the two electron-doped cuprates are nearly the same (16.7 and 16.5 meV) and significantly different from the magnetic resonance energies (9.0 or 10.5 meV) revealed by inelastic neutron scattering experiments [33, 35]. The mode energy of about 16.5 meV, which is independent of doping and T_c, agrees with the energies of the two transverse optical (TO) phonon modes (15.6 meV for the E_u mode and 17.0 meV for the A_{2u}) [42]. This implies that the phonon modes rather than the magnetic-resonance modes mediate electron pairing in electron-doped cuprates. This is also consistent with both ARPES data [43] of hole-doped $\mathrm{Bi_2Sr_2CuO_6}$ and theoretical studies [44, 45], which show that the optical phonons are strongly coupled to electrons due to the unscreened long-range interaction along the c-axis.

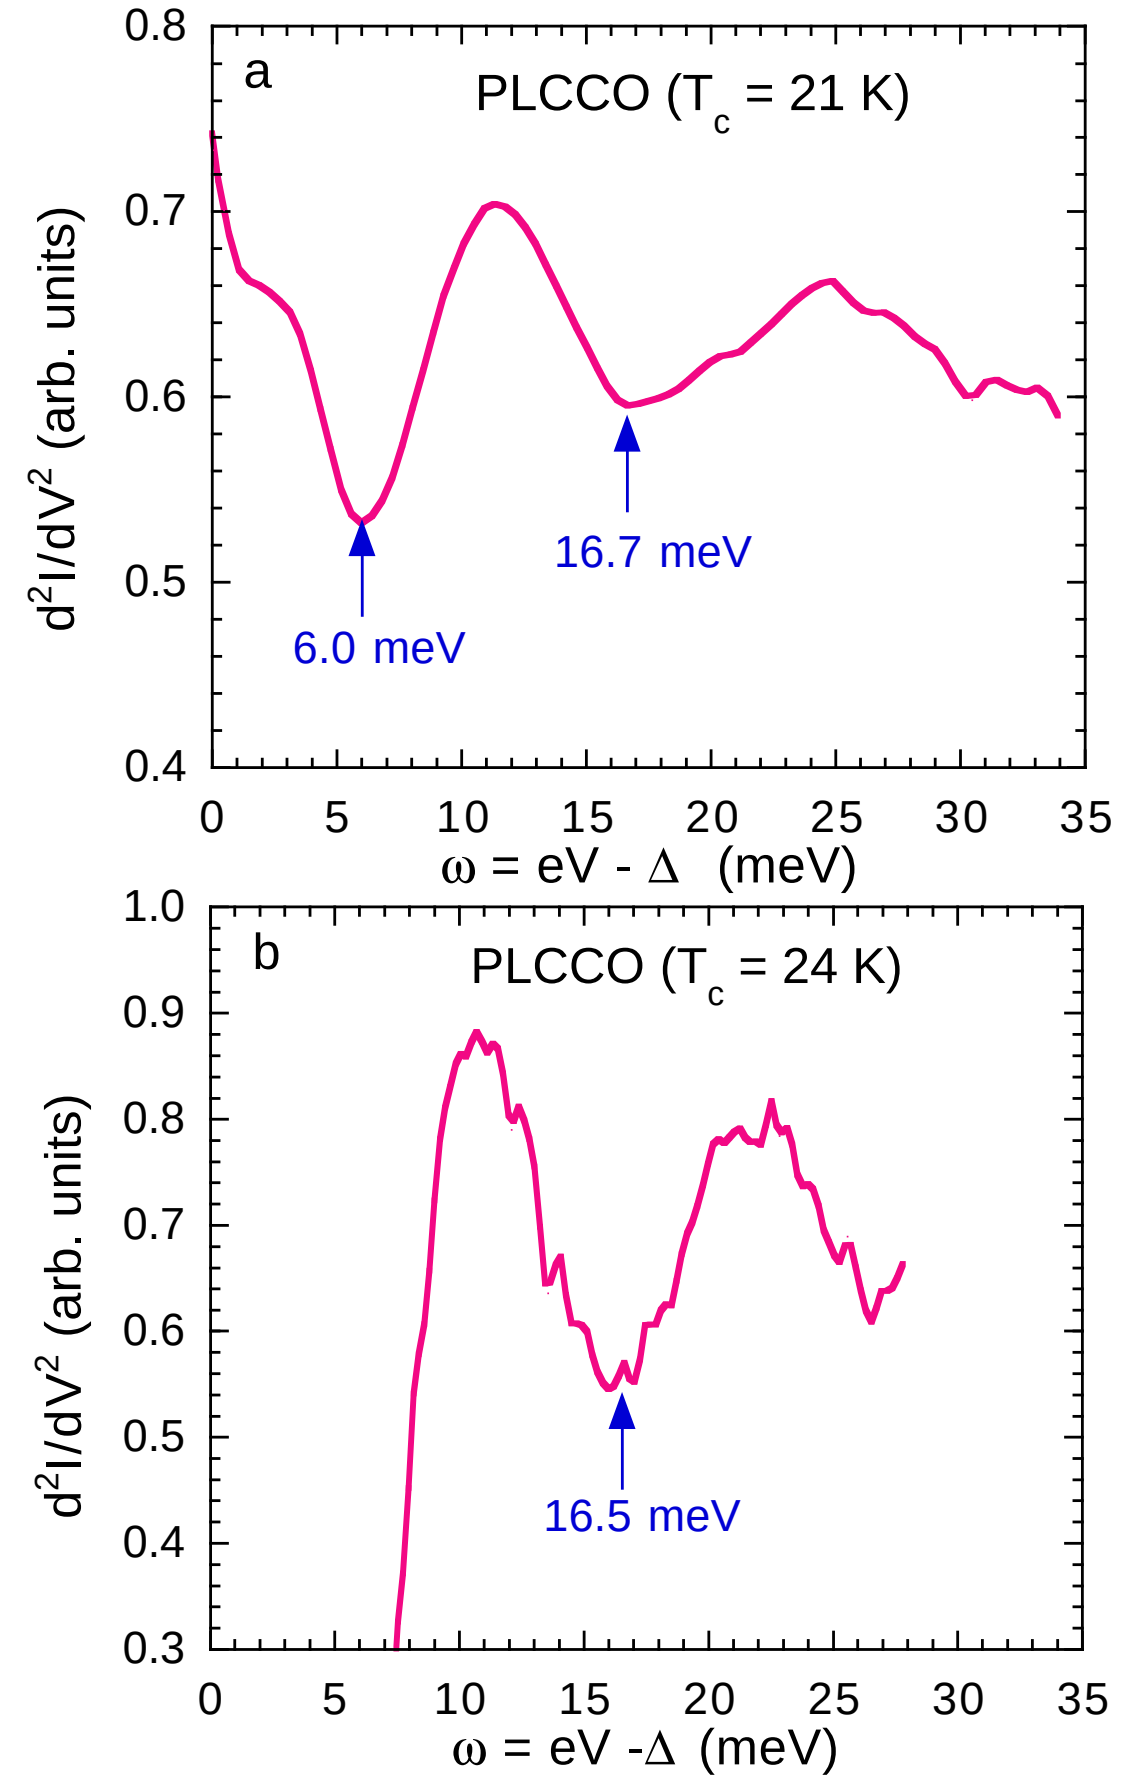

FIG. 1: a) $\mathrm{d}^2I/\mathrm{d}V^2$ spectrum for an electron-doped PLCCO sample with $T_c = 21$ K, which is reproduced from Ref. [35]. b) $\mathrm{d}^2I/\mathrm{d}V^2$ spectrum for an electron-doped PLCCO sample with $T_c = 24$ K, which is reproduced from Ref. [33]. The energy positions of the $\mathrm{d}^2I/\mathrm{d}V^2$ spectra are measured from the superconducting gaps.

It is interesting that in the structurally similar single-layer hole-doped $\mathrm{La_{1.84}Sr_{0.16}CuO_4}$ (LSCO) sample, there is a similar mode with energy of 17.5 meV (see Fig. 2a). The same mode with energy of 16.8 meV is independently revealed in the effective electron-boson spectral function of hole-doped $\mathrm{La_{1.97}Sr_{0.03}CuO_4}$ sample (see Fig. 2b), which was extracted from high-resolution ARPES data [24]. It is striking that the mode energies (5.9 meV, 17.5 meV, and 27.3 meV) inferred from the dip positions of the tunneling spectrum match the peak positions (6.0 meV, 16.8 meV, and 26.9 meV) in the effective electron-boson spectral function independently determined from ARPES data. This further justifies the correctness of our mode assignment. The bosonic mode at about 6.0 meV seen in the overdoped n-type cuprate (Fig. 1a) and in hole-doped $\mathrm{La_{1.84}Sr_{0.16}CuO_4}$ (Fig. 2a)

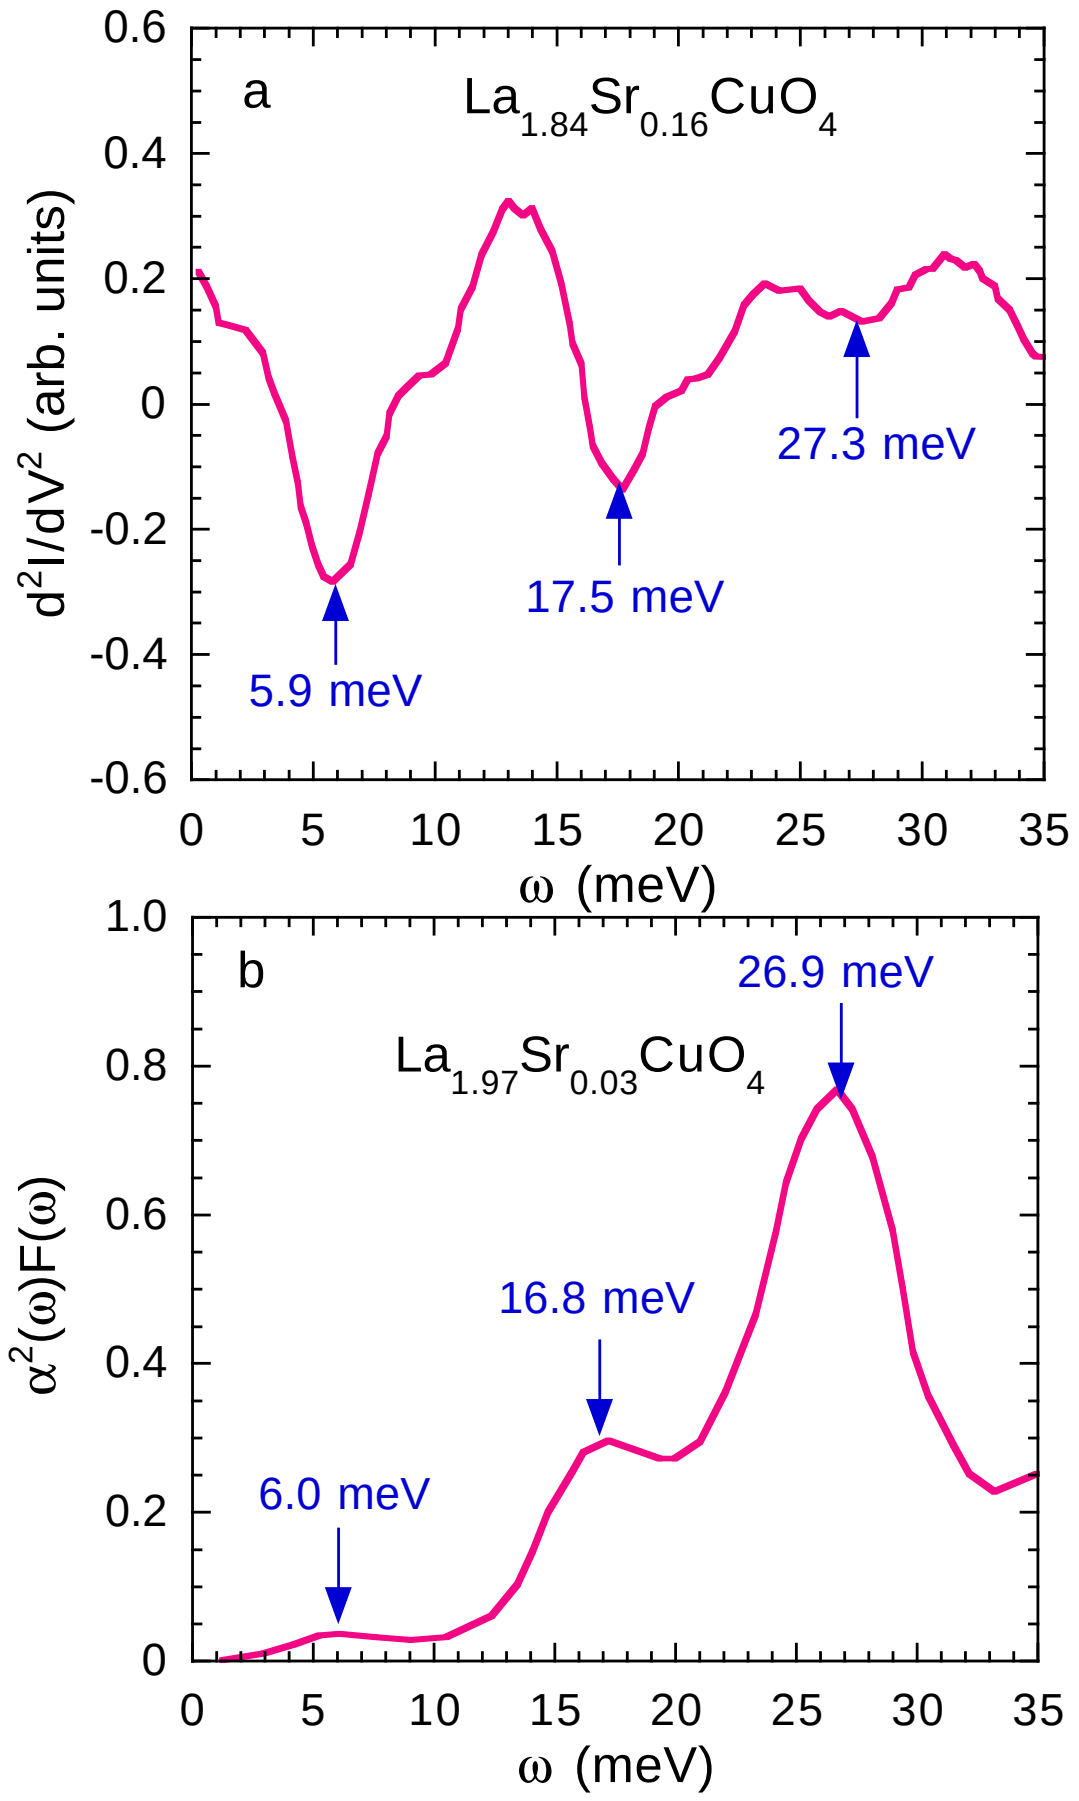

FIG. 2: a) d^2I/dV^2 spectrum at 7.2 K for hole-doped $La_{1.84}Sr_{0.16}CuO_4$, which is reproduced from Fig. 4 of Ref. [29]. The energy position of the d^2I/dV^2 spectrum is measured from the superconducting gap. b) Effective electron-boson spectral function for the hole-doped $La_{1.97}Sr_{0.03}CuO_4$, which is extracted from high-resolution ARPES data. The curve is reproduced from Ref. [24].

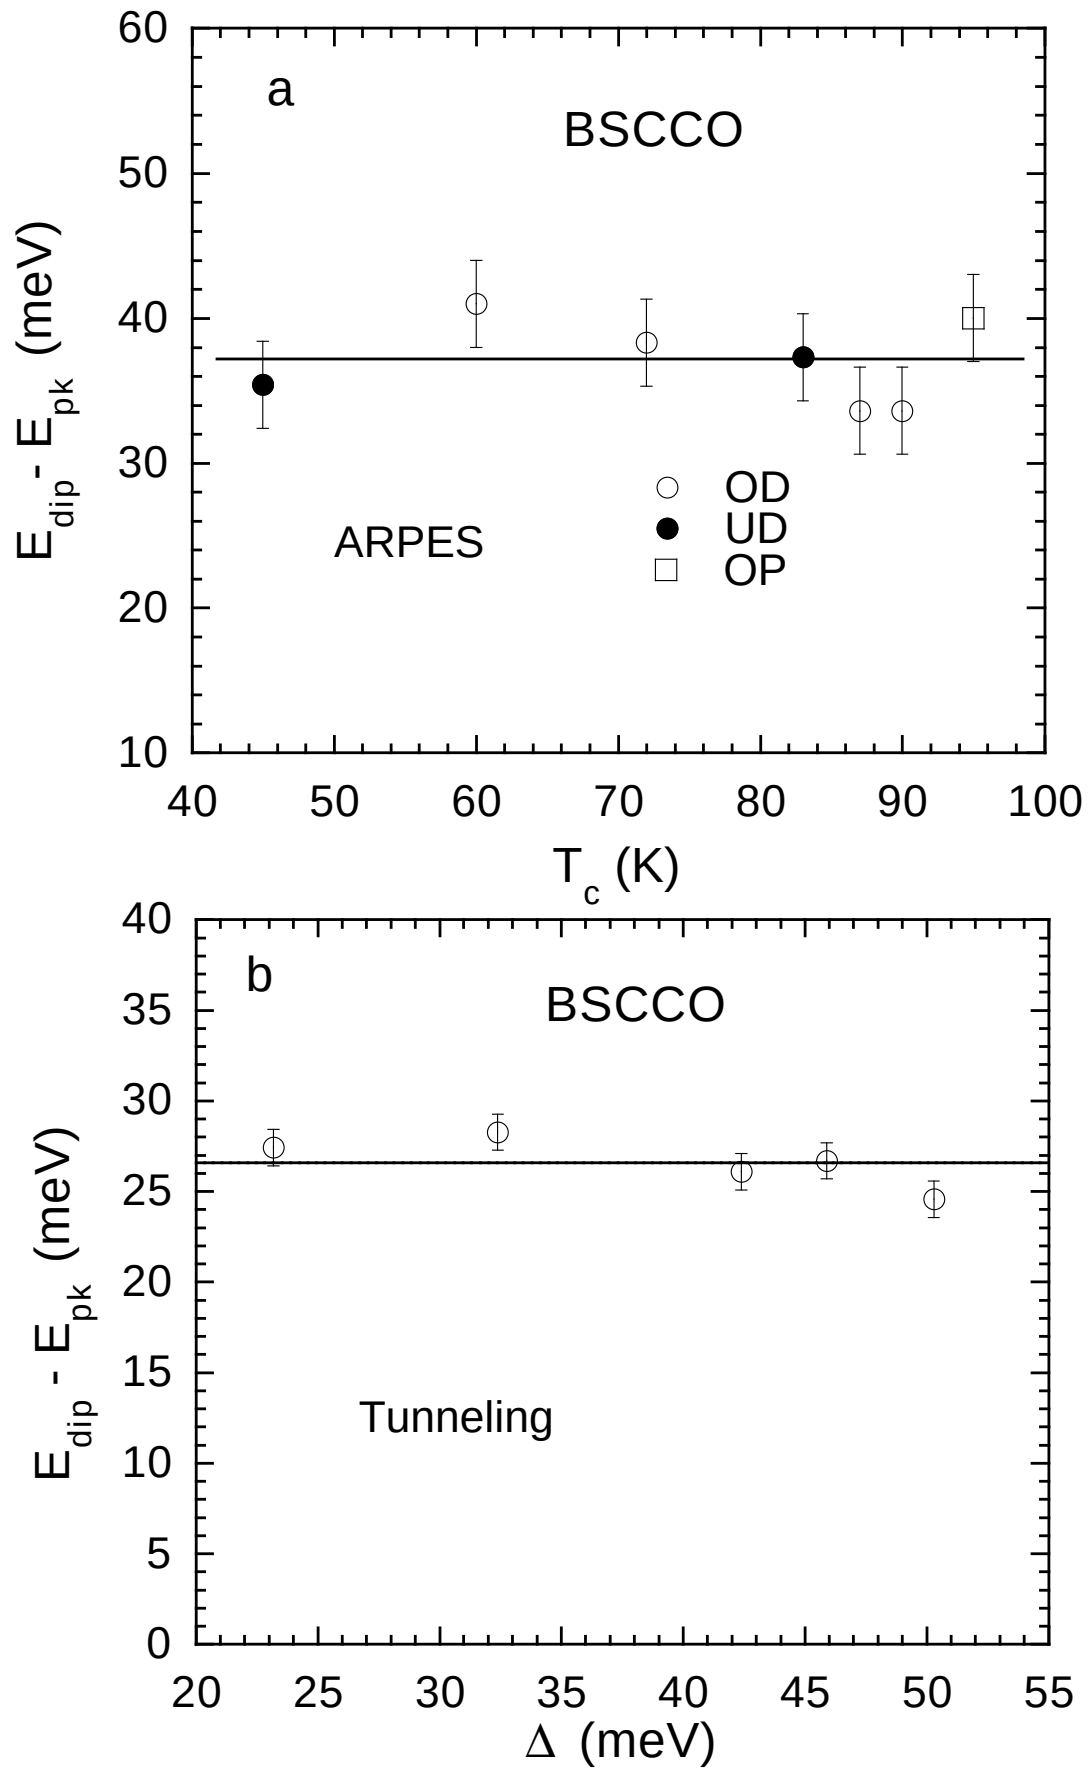

FIG. 3: a) Dependence of $E_{dip} - E_{pk}$ on T_c, which is reproduced from Ref. [11]. The $E_{dip} - E_{pk}$ values were determined from ARPES data. b) Dependence of $E_{dip} - E_{pk}$ on the superconducting gap Δ which is a function of T_c. The $E_{dip} - E_{pk}$ values are obtained from Supplementary Figure 2 of Ref. [49].

and $La_{1.97}Sr_{0.03}CuO_4$ (Fig. 2b) is also seen in the tunneling spectra of $YBa_2Cu_3O_7$ and $Bi_2Sr_2CaCu_2O_8$ (Ref. [28]). This indicates that this mode is universal for the cuprate systems and cannot originate from antiferromagnetic fluctuations.

Since the magnetic-resonance mode energy was found [46] to be proportional to T_c, insensitivity of the mode energies to T_c further argues against the magnetic origin of the modes. The similar mode energies across different doping levels (Fig. 2) and across different single-layer structures (PLCCO and LSCO) are consistent with the phonon mode assignment and contradict the magnetic mode assignment.

For double-layer cuprates such as $Bi_2Sr_2CaCu_2O_{8+y}$, strong coupling to the magnetic resonance mode was expected to produce a peak-dip-hump (PDH) structure in ARPES spectra along the antinodal direction [47]. This PDH structure was also predicted to be present in dI/dV tunneling spectra [48]. The energy separation between the dip and peak features is exactly equal to the energy E_r of the magnetic resonance mode [47, 48], that is, $E_{dip} - E_{pk} = E_r$. Since E_r was found [46] to be proportional to T_c, $E_{dip} - E_{pk}$ should also be proportional to T_c. This is in sharp contrast to the experimental results shown in Fig. 3. The $E_{dip} - E_{pk}$ values obtained from ARPES (Fig. 3a) and tunneling spectra (Fig. 3b) are nearly independent of doping or T_c, in contradiction with the theoretical predictions based on the d-wave magnetic pairing mechanism. Furthermore, the constant $E_{dip} - E_{pk}$ values (see the horizontal solid lines) obtained from ARPES and tunneling data differ by about 10 meV. Because ARPES is probing the average property of the whole top layer while the spatially-resolved tunneling spectrum is measuring the local property of nanosized range, the coherence peaks in tunneling spectra are much sharper than those in ARPES. This may explain why the dips in tunneling spectra are pushed more towards the peaks than those in ARPES.

Another important issue is the intrinsic pairing (gap) symmetry in the bulk of superconducting cuprates. Because nearly all the surface and phase-sensitive experiments for both electron- and hole-doped cuprates provide clear evidence for *d*-wave order-parameter (OP) symmetry [3], the *d*-wave pairing symmetry has become an indisputable fact for most researchers in the field. However, it is important to note that the pairing symmetry is not necessarily the same as the OP symmetry. In particular when superconductivity arises from the Bose-Einstein condensate of local pairs, the OP symmetry could be different from the pairing symmetry [50]. In fact, these surface- and phase-sensitive experiments based on planar Josephson tunneling are probing the OP symmetry at surfaces and interfaces which were found to be underdoped [51, 52]. Since the majority of charge carriers are oxygen-hole bipolarons in the underdoped regime [53, 54] and the OP symmetry of the Bose-Einstein condensate of the oxygen-hole bipolarons was predicted to be *d*-wave [50], the phase-sensitive experiments just probe the *d*-wave OP symmetry of the bipolaron condensate rather than the pairing (gap) symmetry. Since the symmetry of the Bose-Einstein condensate has nothing to do with the pairing symmetry, the phase-sensitive experiments do not probe the pairing symmetry associated with the pairing interaction. To probe the intrinsic pairing symmetry, bulk-sensitive data should be obtained from significantly overdoped samples where the dominant charge carriers are Fermi-liquid like and the superconducting transition is BCS-like [11]. Based on the quantitative analyses of many bulk-sensitive experiments (in addition to some bulk- and phase-sensitive experiments such as nonmagnetic pair-breaking effects), we have concluded that the intrinsic pairing symmetry in the bulk of cuprates is not *d*-wave, but extended s-wave (having eight line nodes) in hole-doped cuprates [55] and nodeless s-wave in electron-doped cuprates [55–57].

In summary, our analyses of tunneling spectra and their comparison with ARPES data in both electron and hole doped cuprates have unambiguously ruled out magnetic pairing mechanism. Our conclusion is further supported by the recent pump-probe spectroscopy [19, 58] showing that T_c is sensitive to the electron-phonon interaction and by the Raman measurements showing that T_c is insensitive to magnetic interactions in high-T_c superconductors [59]. The polaron-bipolaron theory of superconductivity, which is based on realistic electron-electron correlation and long-range electron-phonon interaction, is compatible with many experimental results including the Cooper pairing and large Fermi surface observed in optimally doped and overdoped cuprates as well as *d*-wave order parameter symmetry for underdoped cuprates.

---

* gzhao2@calstatela.edu

[1] J. G. Bednorz and K. A. Müller, Z. Phys. B: Condens. Matter **64**, 189 (1986).

[2] For a recent review see N. Plakida, *High temperature cuprate superconductors: experiment, theory and applications* (Springer, Heidelberg 2010).

[3] C. C. Tsuei and J. R. Kirtley, Rev. Mod. Phys. **72**, 969 (2000).

[4] For a recent review see A. S. Alexandrov and J. T. Devreese, *Advances in Polaron Physics* (Springer, Berlin 2009).

[5] G. M. Zhao, K. K. Singh, and D. E. Morris, Phys. Rev. B **50**, 4112 (1994).

[6] G. M. Zhao and D. E. Morris, Phys. Rev. B **51**, 16487(R) (1995).

[7] G. M. Zhao, K. K. Singh, A. P. B. Sinha, and D. E. Morris, Phys. Rev. B **52**, 6840 (1995).

[8] G. M. Zhao, M. B. Hunt, H. Keller, and K. A. Müller, Nature (London) **385**, 236 (1997).

[9] G. M. Zhao, K. Conder, H. Keller, and K. A. Müller, J. Phys.: Condens. Matter **10**, 9055 (1998).

[10] G. M. Zhao, H. Keller, and K. Conder, J. Phys.: Condens. Matter **13**, R569 (2001).

[11] G. M. Zhao, Phil. Mag. B **81**, 1335 (2001).

[12] G. M. Zhao, V. Kirtikar, and D. E. Morris, Phys. Rev. B **63**, 220506(R) (2001).

[13] R. Khasanov, D. G. Eshchenko, H. Luetkens, E. Morenzoni, T. Prokscha, A. Suter, N. Garifianov, M. Mali, J. Roos, K. Conder, and H. Keller, Phys. Rev. Lett. **92**, 057602 (2004).

[14] R. J. McQueeney, Y. Petrov, T. Egami, M. Yethiraj, G. Shirane, and Y. Endoh, Phys. Rev. Lett. **82**, 628 (1999).

[15] T. R. Sendyka, W. Dmowski, T. Egami, N. Seiji, H. Yamauchi, and S. Tanaka, Phys. Rev. B **51**, 6747 (1995).

[16] D. Reznik, L. Pintschovius, M. Ito, S. Iikubo, M. Sato, H. Goka, M. Fujita, K. Yamada, G. D. Gu, and J. M. Tranquada, Nature (London) **440**, 1170 (2006).

[17] A. Lanzara, P. V. Bogdanov, X. J. Zhou, S. A. Kellar, D. L. Feng, E. D. Lu, T. Yoshida, H. Eisaki, A. Fujimori, K. Kishio, J.-I. Shimoyama, T. Noda, S. Uchida, Z. Hussain, and Z.-X. Shen, Nature (London) **412**, 510 (2001).

[18] O. Rösch, O. Gunnarsson, X. J. Zhou, T. Yoshida, T. Sasagawa, A. Fujimori, Z. Hussain, Z.-X. Shen, and S. Uchida, Phys. Rev. Lett. **95** 227002 (2005).

[19] C. Gadermaier, A. S. Alexandrov, V. V. Kabanov, P. Kusar, T. Mertelj, X. Yao, C. Manzoni, D. Brida, G. Cerullo, and D. Mihailovic, Phys. Rev. Lett. **105**, 257001 (2010).

[20] D. Mihailovic, C. M. Foster, K. Voss, and A. J. Heeger, Phys. Rev. B 42, 7989 (1990).

[21] O. V. Misochko, E. Ya. Sherman, N. Umesaki, K. Sakai, S. Nakashima, Phys. Rev. B **59**, 11495 (1999).

[22] Y. S. Lee, K. Segawa, Z. Q. Li, W. J. Padilla, M. Dumm, S. V. Dordevic, C. C. Homes, Yoichi Ando, and D. N. Basov, Phys. Rev. B **72**, 054529 (2005).

[23] A. S. Mishchenko, N. Nagaosa, Z.-X. Shen, G. De Filippis, V. Cataudella, T. P. Devereaux, C. Bernhard, K. W. Kim, and J. Zaanen, Phys. Rev. Lett. **100**, 166401 (2008).

[24] X. J. Zhou *et al.*, Phys. Rev. Lett. **95**, 117001 (2005).

[25] S. I. Vedeneev, P. Samuely, S. V. Meshkov, G. M. Eliashberg, A. G. M. Jansen, and P. Wyder, Physica C **198**, 47 (1992).

[26] D. Shimada, Y. Shiina, A. Mottate, Y. Ohyagi, and N. Tsuda, Phys. Rev. B **51**, 16495 (1995); D. Shimada, N. Tsuda, U. Paltzer, F. W. de Wette, Physica C **298**, 195 (1998).

[27] R. S. Gonnelli, G. A. Ummarino, and V. A. Stepanov, Physica C **275**, 162 (1997).

[28] G. M. Zhao, Phys. Rev. B **75**, 214507 (2007).

[29] H. Shim, P. Chaudhari, G. Logvenov and I. Bozovic, Phys. Rev. Lett. **101**, 247004 (2008).

[30] G. M. Zhao, Phys. Rev. Lett **103**, 236403 (2009).

[31] A. S. Alexandrov, EPL **95**, 27004 (2011).

[32] A. S. Alexandrov, J. H. Samson, and G. Sica, cond-mat/arXiv:1205.3436

[33] F. C. Niestemski, S. Kunwar, S. Zhou, S. L. Li, H. Ding, Z. Q. Wang, P. C. Dai, and V. Madhavan, Nature (London) **450**, 1058 (2007).

[34] T. Dahm, V. Hinkov, S. V. Borisenko, A. A. Kordyuk, V. B. Zabolotnyy, J. Fink, B. Buchner, D. J. Scalapino, W. Hanke, and B. Keimer, Nature Phys. **5**, 780 (2009).

[35] Jun Zhao, F. C. Niestemski, Shankar Kunwar, Shiliang Li, P. Steffens, A. Hiess, H. J. Kang, Stephen D. Wilson, Ziqiang Wang, Pengcheng Dai1, and V. Madhavan, Nature Phys. **7**, 719 (2011).

[36] G. M. Zhao, Phys. Scr. **83**, 038304 (2011).

[37] A. S. Alexandrov and V. V. Kabanov, Phys. Rev. Lett. 106, 136403 (2011).

[38] T. Aimi and M. J. Imada, Phys. Soc. Jpn. **76**, 113708 (2007).

[39] T. M. Hardy, J. P. Hague, J. H. Samson, and A. S. Alexandrov, Phys. Rev. B **79**, 212501 (2009).

[40] W. L. McMillan and J. M. Rowell, Phys. Rev. Lett. 14, 108 (1965).

[41] J. P. Carbotte, Rev. Mod. Phys. **62**, 1027 (1990); W. L. McMillan and J. M. Rowell, in *Superconductivity*, edited by R. D. Parks, (Marcel Dekker, New York, 1969), Vol. 1, p. 561; E. L. Wolf, *Principles of electron tunneling spectroscopy*, (Oxford University Press, New York, 1985).

[42] M. K. Crawford, G. Burns, G. V. Chandrashekhar, F. H. Dacol, W. E. Farneth, E. M. McCarron, III and R. J. Smalley, Solid State Commun. **73**, 507 (1990).

[43] W. Meevasana, N. J. C. Ingle, D. H. Lu, J. R. Shi, F Baumberger, K. M. Shen, W. S. Lee, T. Cuk, H. Eisaki,T. P. Devereaux, N. Nagaosa, J. Zaanen, and Z.-X. Shen, Phys. Rev. Lett. 96, 157003 (2006).

[44] W. Meevasana, T.P. Devereaux, N. Nagaosa, Z.-X. Shen, and J. Zaanen, Phys. Rev. B **74**, 174524 (2006).

[45] T. Bauer and C. Falter, Phys. Rev. B **80**, 094525 (2009).

[46] Jun Zhao, Pengcheng Dai, Shiliang Li, Paul G. Freeman, Y. Onose, and Y. Tokura, Phys. Rev. Lett. **99**, 017001 (2007).

[47] A. Abanov and A. V. Chubukov, Phys. Rev. Lett. bf 83, 1652 (1999).

[48] J. F. Zasadzinski, L. Coffey, P. Romano, and Z. Yusof, Phys. Rev. B **68**, 180504(R) (2003).

[49] J.-H. Lee, K. Fujita, K. McElroy, J. A. Slezak, M. Wang, Y. Aiura, H. Bando, M. Ishikado, T. Masui, J.-X. Zhu, A. V. Balatsky, H. Eisaki, S. Uchida, and J. C. Davis, Nature **442**, 546 (2006).

[50] A.S. Alexandrov, Physica C **305**, 46 (1998).

[51] J. Betouras and R. Joynt, Physica C **250**, 256 (1995).

[52] J. Mannhart and H. Hilgenkamp, Physica C **317-318**, 383 (1999).

[53] G. M. Zhao, Phys. Scr. **83**, 038302 (2011).

[54] A. S. Alexandrov and G. M. Zhao, New Journal of Physics **14**, 013046 (2012).

[55] G. M. Zhao, Phys. Rev. B **64**, 024503 (2001).

[56] G. M. Zhao, Phys. Rev. B **82**, 012506 (2010).

[57] G. M. Zhao and J. Wang, J. Phys.: Condens. Matter **22** 352202 (2010).

[58] C. Gadermaier, V. V. Kabanov, A. S. Alexandrov, L. Stojchevska, T. Mertelj, C. Manzoni, G. Cerullo, N. D. Zhigadlo, J. Karpinski, Y. Q. Cai, X. Yao, Y. Toda, M. Oda, S. Sugai, and D. Mihailovic, arXiv:1205.4978.

[59] B. Mallett, G.V.M. Williams, A.B. Kaiser, E. Gilioli, F. Licci, T. Wolf, and J.L. Tallon, arXiv:1202.5078